

LANXESS DEUTSCHLAND GMBH
HIGH PERFORMANCE MATERIALS BUSINESS UNIT
D-50569 COLOGNE | WWW.LANXESS.COM

This information and our technical advice - whether verbal, in writing or by way of trials - are given in good faith but without warranty, and this also applies where proprietary rights of third parties are involved. Our advice does not release you from the obligation to verify the information currently provided - especially that contained in our safety data and technical information sheets - and to test our products as to their suitability for the intended processes and uses. The application, use and processing of our products and the products manufactured by you on the basis of our technical advice are beyond our control and, therefore, entirely your own responsibility.

Trial Products (grade designations beginning with the code TP) are sales products at the developmental stage. For this reason, no assurances can be given as to type conformity, processability, long-term performance characteristics or other production or application parameters. No definitive statements can be made regarding the behavior of the product during processing or use. The purchaser/user uses the product entirely at his own risk. The marketing and continued supply of this material are not assured and may be discontinued at any time.

Our products are sold in accordance with the current version of our General Conditions of Sale and Delivery.

Order No.: LXS-HPM-073EN, Edition: 2016-10
© = LANXESS Deutschland GmbH 2016 | all rights reserved



HIGHTECH THERMOPLASTICS ENERGIZED BY



**High-Tech Thermoplastics for the E&E Industry
Standards, Testing, Materials, Applications**

X Durethan® X Pocan® X HiAnt®

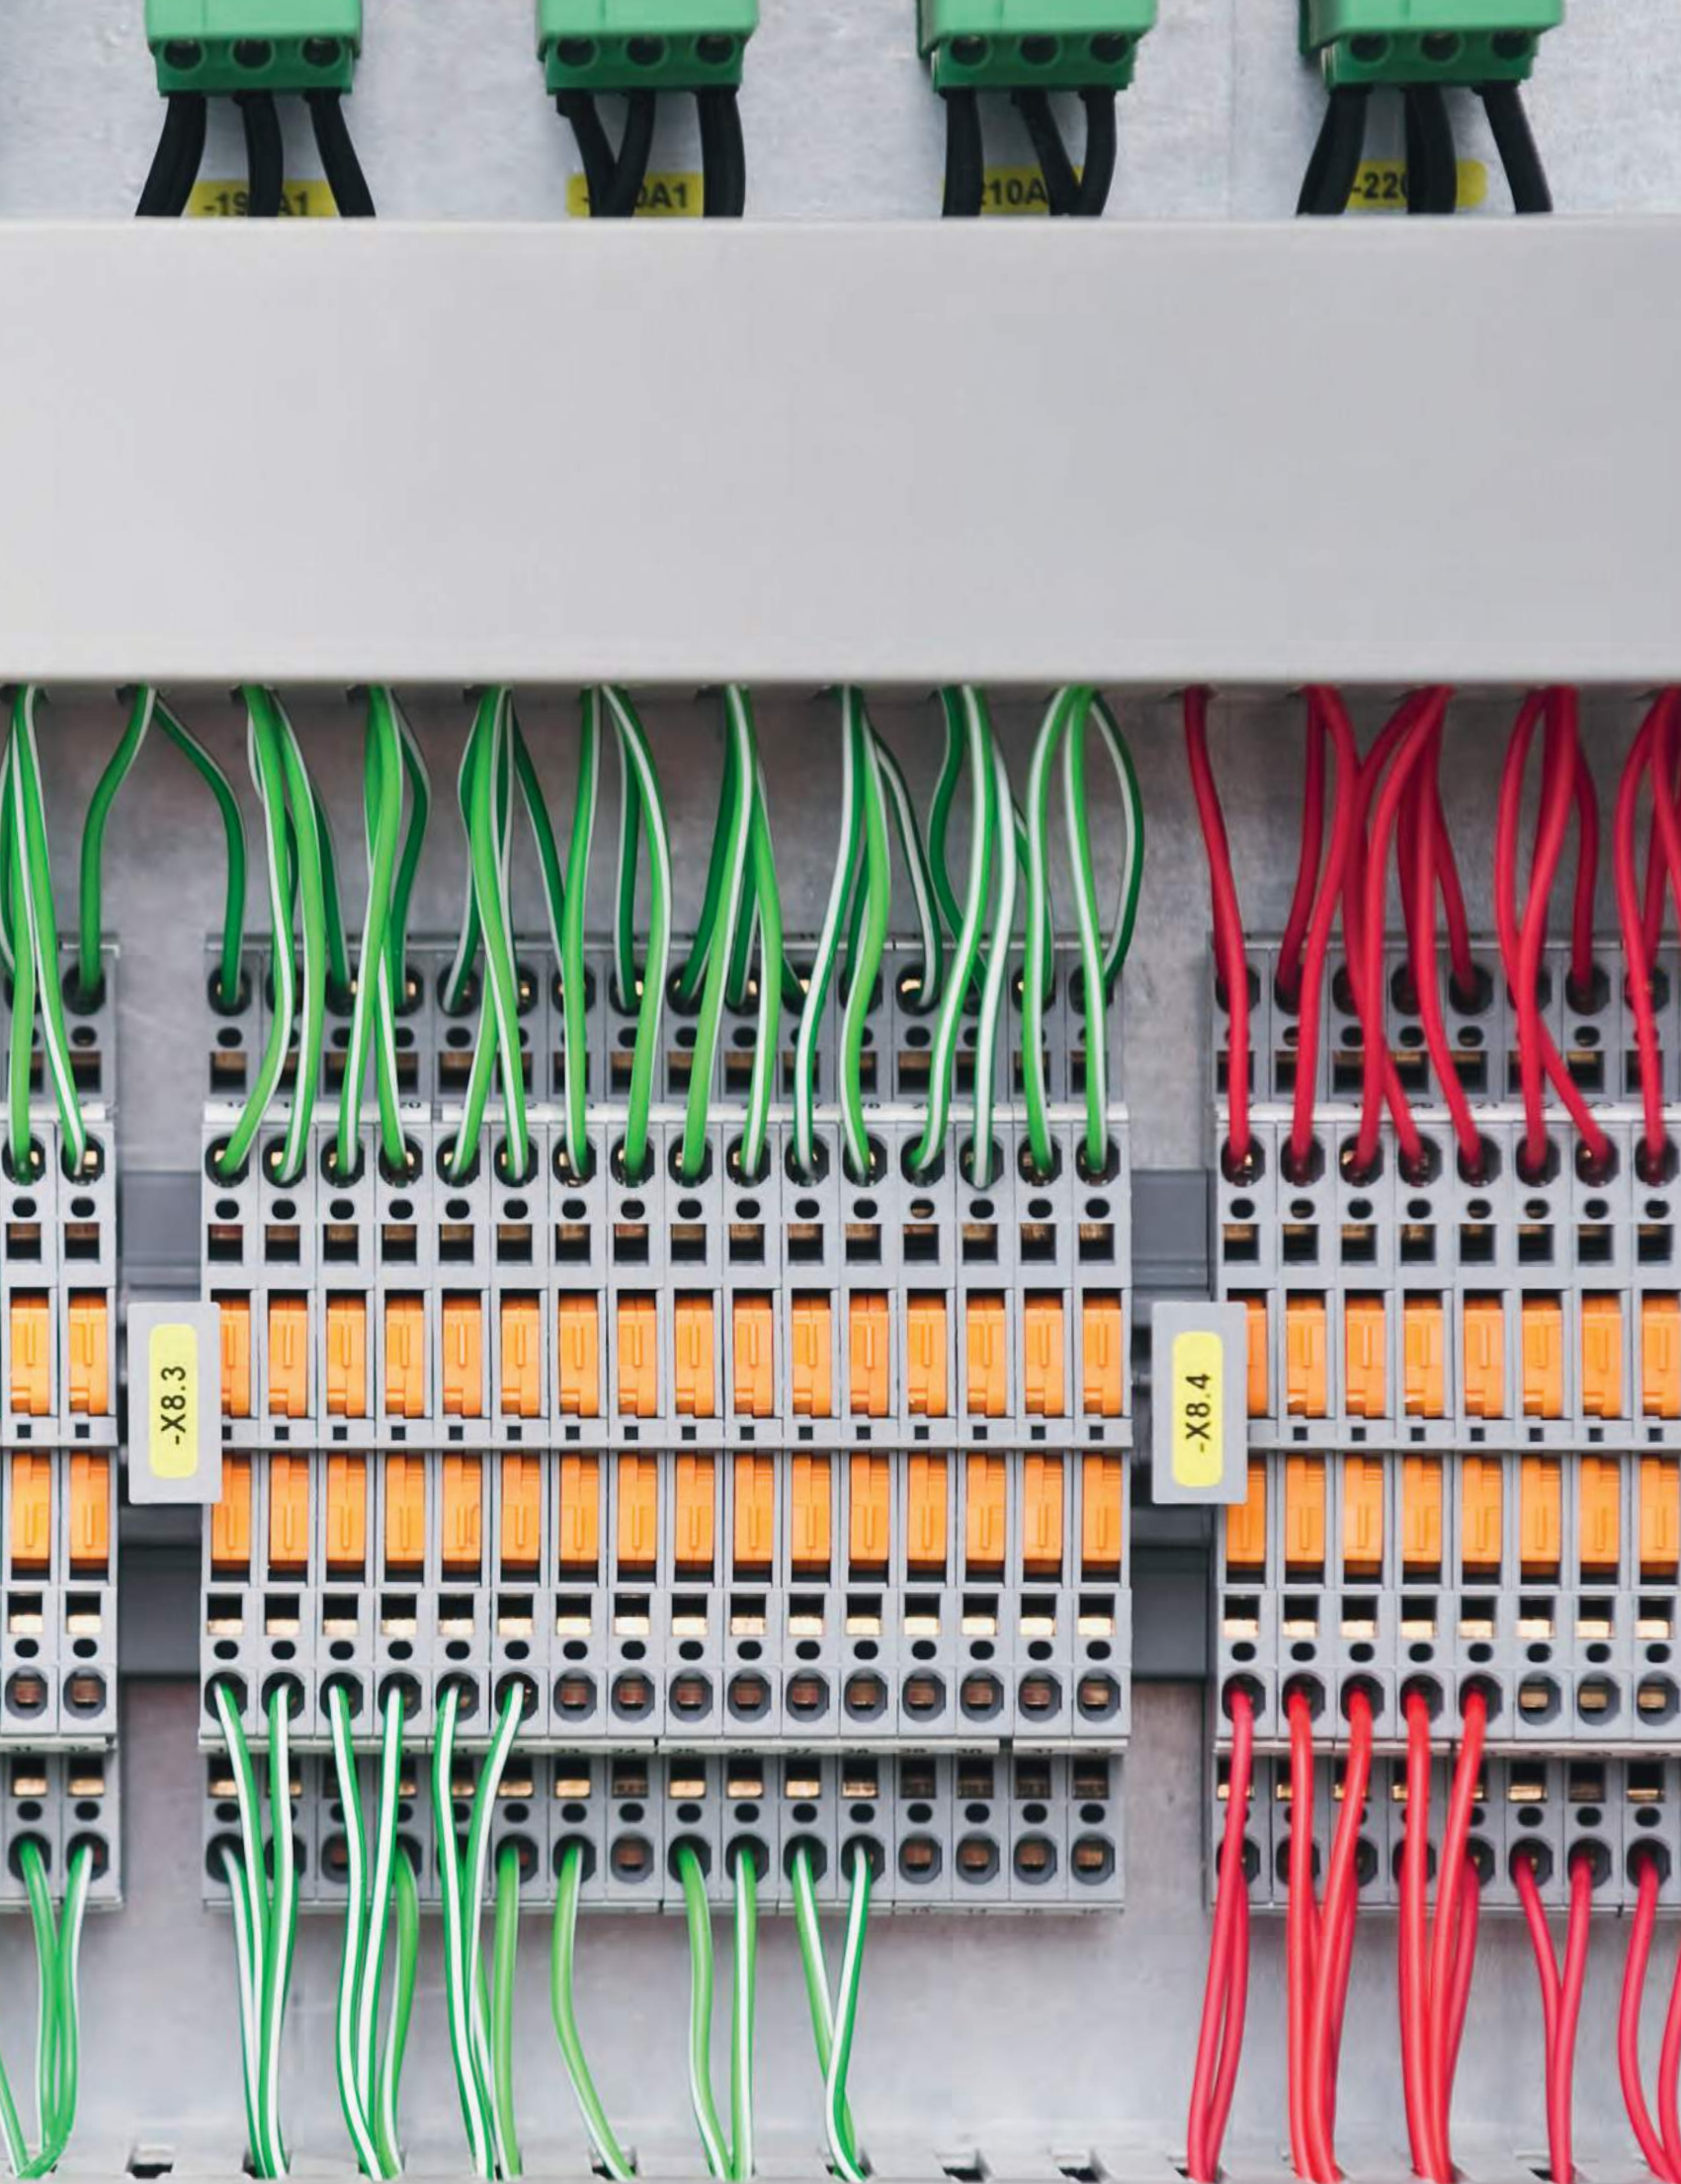


TABLE OF CONTENTS

04	THE INTERNATIONAL E&E SEGMENT – OUR PARTNER INDUSTRY
05	OUR AREAS OF EXPERTISE – A BROAD SPECTRUM
05	THERMOPLASTICS – PROVEN PERFORMERS IN E&E APPLICATIONS
06	OUR EXPERTISE – SAFETY WITH ADDED VALUE
08	SELECTED APPLICATION-RELATED STANDARDS – AN OVERVIEW
13	SELECTED TEST METHODS – AN OVERVIEW
13 – 17	Flame retardance tests
17 – 21	Electrical behavior testing
22	Testing of long-term thermal resistance
22 – 23	Determining thermal conductivity and diffusivity
23	Determining reflectivity
24	FLAME RETARDANTS AND FIRE PROTECTION – AN OVERVIEW
26	OUR THERMOPLASTICS
26	The product range for the E&E industry
27 – 29	Selected innovative materials
30	HIANT®– CUSTOM SERVICES FOR THE E&E INDUSTRY
31	LIST OF IMPORTANT STANDARDS

THE INTERNATIONAL E&E SEGMENT – OUR PARTNER INDUSTRY

Whether it's Industry 4.0, digital networking of smart home technology, domestic appliances and entertainment electronics, or intelligent power grids for the energy revolution, IT security or electric mobility – practically all key issues of the future and megatrends worldwide depend on innovations in the area of electrical and electronics (E&E). And plastics have a vital role to play in these developments. They are among the most important design materials for E&E components. That's why LANXESS offers the growth industry E&E a range of innovative **Durethan®** and **Pocan®** brand thermoplastic materials that meet the latest requirements.

The specialty chemicals company makes it a top priority to ensure its materials fulfill the E&E industry's international standards – whether used in components for industrial applications, household appliances, LED lighting technology, consumer and home electronics, or power tools. And LANXESS also collaborates closely with partners from the E&E industry, providing new materials and technologies to help realize development trend breakthroughs.

OUR AREAS OF EXPERTISE – A BROAD SPECTRUM

With production plants in all important trade regions, LANXESS is a leading supplier of products including compounds based on polyamide 6 and polyamide 66, as well as polyesters like polybutylene terephthalate (PBT). It is exactly these plastics that are very widely used in the production of E&E components. So LANXESS clearly has decades of experience with the E&E industry. Furthermore, our experts serve on important committees and in organizations for standards and testing – for example UL and TC 89 – and thus have extensive knowledge of the industry's needs, particularly when it comes to electrical and fire safety.

We stand out from most of our competitors thanks to our in-depth know-how in development of materials, applications, processes and technology. We have combined all that in the **HiAnt®** brand, thus helping customers at all levels of application development – from the concept phase and materials optimization to the start of series production. Unlike most of our competitors, we are highly backward-integrated in the value chain of our high-tech plastics. For example, we produce our own glass fibers for our compounds and raw materials for polyamide 6, at world-scale facilities.

Overall, our customers in the E&E sector benefit from:

- optimal reliability of supply and delivery
- controlled production costs for our plastics
- the certified high quality of our products, uniform worldwide
- development know-how focused on the E&E industry
- a network of regional and local centers for development of products and applications, spanning the globe and close to our customers
- **HiAnt®** custom services for customer needs in all stages of component development

THERMOPLASTICS – PROVEN PERFORMERS IN E&E APPLICATIONS

The electrical insulation properties of our thermoplastics offer a major advantage in E&E applications. Also highly valued by customers are not only the great design flexibility they allow in the design of components, but also possibilities for integrating functions by means of injection molding. Direct integration of guides, fastening elements or retainers, for example, simplifies subsequent assembly and reduces logistics costs, which also means lower production costs. Design freedom, integration of functions and light weight are the reasons that thermoplastics have become established as the E&E industry's material of choice in many E&E applications. This is also due to freedom of design in terms of color and surface structure, and the excellent surface quality and coatability of the plastic components. Fiber-reinforced thermoplastics enable production of structural components that are lighter but still also display excellent mechanical strength.



OUR EXPERTISE – SAFETY WITH ADDED VALUE

Plastics are generally flammable. So they must offer the highest degree of electrical safety and fire safety. In many E&E applications (but by no means all), this requires use of flame-retardant materials, although specifications for flame retardance can vary greatly depending on the specific application. The requirements are defined in national and international standards, regulations and guidelines, which specify test methods a plastic must be able to stand up to. Whether or not the product will even be considered for certain E&E applications is determined above all by its ability to pass certain tests.

This is why our polyamides and polyesters for safety-relevant E&E applications are developed primarily with these test methods in mind. In doing so, we simultaneously take into account ecological, commercial and market-specific factors. That is in addition to findings and experience we have gained from our participation in standardization bodies, e.g. for fire safety.

We take a very targeted approach to ensuring our materials that contain flame-retardant additives (and those free of them) provide further benefits offering added value to our customers. These include the following examples:

- a wide processing window
- good flowability
- excellent thermal resistance
- excellent thermal conductivity
- excellent light stability and light reflection
- good suitability for welding and laser marking



SELECTED APPLICATION-RELATED STANDARDS – AN OVERVIEW

In this section we present the most important standards and test methods, because they play a crucial role in the selection of plastics for E&E applications.

UL – Yellow Card

The U.S.-based testing organization Underwriters Laboratories (UL) tests products to certify their safety. Passing the UL tests is mandatory for electrical devices and appliances intended for use in the American market, but it is often required in other countries as well. Plastics manufacturers commission

UL to systematically evaluate their products intended for use in electrical components and finished parts. This involves optional testing particularly of their flame retardance, electrical behavior and continuous use temperatures. The test results are documented on what is known as the “Yellow Card.” Manufacturers of electrical components can use the card to find plastics suitable for their needs, while also reducing testing costs for a UL certification. The Yellow Cards for the relevant **Durethan®** and **Pocan®** types are listed at UL under the LANXESS file number E245249.



UL 746C – “Standard for Polymeric Materials – Use in Electrical Equipment Evaluations”


Within the scope of UL applicability, plastic used as an insulating material in electric components must pass various flammability and ignition tests. These are specified in the UL 746C¹ standard. The specific performance required of the individual plastic is determined also by where the appliance/device will be used. The requirements vary depending on whether the device or appliance is used in indoor spaces or outdoors, and whether or not it is exposed to severe weathering and soiling. Certification in accordance with UL 746C is based on fire classification in accordance with UL 94 (V-0 to HB) and on the results of the Hot Wire Ignition (HWI) test and the High Amp Arc Ignition (HAI) test.

Flammability and ignition tests for plastics in E/E applications (in accordance with UL 746C)

		HWI					
		PLC 0	PLC 1	PLC 2	PLC 3	PLC 4	PLC 5
HAI	PLC 0	Black	Black	Black	Grey	Orange	White
	PLC 1	Black	Black	Black	Grey	Orange	White
	PLC 2	Red	Red	Red	Grey	Orange	White
	PLC 3	Orange	Orange	Orange	Orange	Orange	White
	PLC 4	White	White	White	White	White	White

Permissible combinations

Black	V-0	V-1	V-2	HB
Red	V-0	V-1	V-2	
Grey	V-0	V-1		
Orange	V-0			

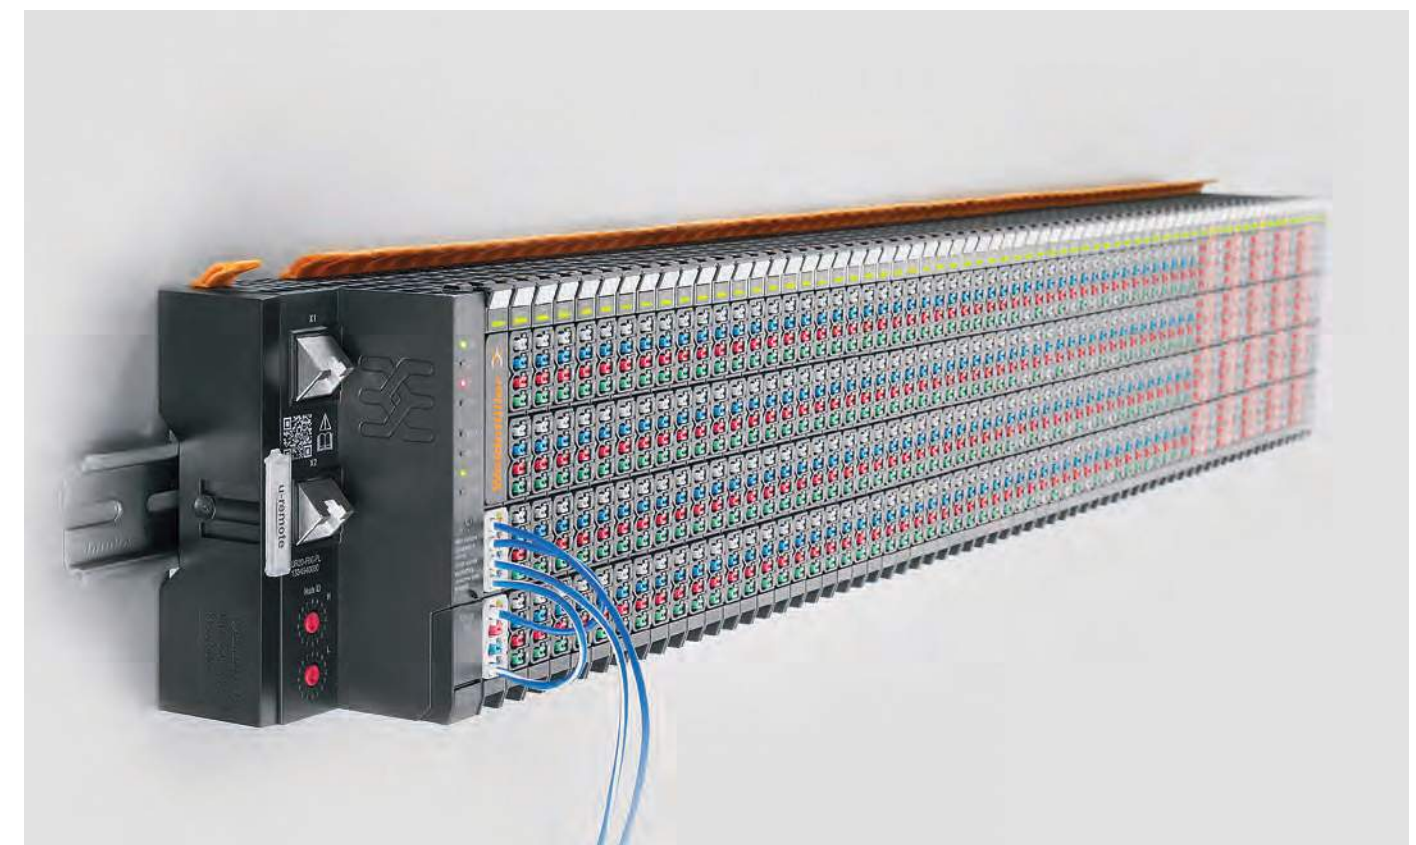

SELECTED APPLICATION-RELATED STANDARDS – AN OVERVIEW

DIN EN 60664-1 – “Insulation coordination for equipment within low-voltage systems”

This standard specifies, among other things, the requirements for air clearances, tracking distances and fixed insulation of equipment. A susceptibility to formation of tracking distances depends on the properties of a plastic and is described by means of the Comparative Tracking Index (CTI). In accordance with DIN EN 60664-1², plastics are divided into Insulation Material Groups. The CTI is determined in accordance with IEC 60112¹⁵.

Insulation Material Group I:	$600 \leq \text{CTI}$
Insulation Material Group II:	$400 \leq \text{CTI} < 600$
Insulation Material Group IIIa:	$175 \leq \text{CTI} < 400$
Insulation Material Group IIIb:	$175 \leq \text{CTI} < 175$

DIN EN 60335-1 – “Household and similar electrical appliances – Safety”


The extended DIN EN 60335-1³ standard for domestic appliances covers electrical, mechanical and thermal hazards, as well as fire and radiation hazards related to household electrical appliances and similar products. Section 30 of the standard summarizes the requirements for heat resistance and fire resistance. The flame retardance of the insulation ma-

terial is tested by means of glow-wire tests in accordance with IEC 60695. Which requirements must be fulfilled depends on the current in the appliance and on its mode of operation (supervised or unsupervised).

The most stringent requirements apply to insulation materials in unsupervised appliances with rated currents above 0.2 ampere (see the graphic). Plastics used in such applications must categorically pass a glow-wire ignition temperature test in accordance with IEC 60695-2-12^{4b} (GWFI, Glow Wire Flammability Index, afterburn duration max. 30 seconds) at 850 °C. In addition, a glow-wire test on test plates must be fulfilled in accordance with IEC 60695-2-13^{4c} (GWIT, Glow Wire Ignition Temperature, max. combustion duration with flame formation five seconds) at 775 °C. If this test is not passed, a test on the finished part in accordance with IEC 60695-2-11^{4a} (GWEPT – Glow Wire End Product Test) can be conducted instead. For this method, the temperature must reach 750 °C, however it involves more rigorous conditions (max. afterburn duration of two seconds permitted). Alternatively, certification is possible if the surrounding components meet at least the requirements of Class V-1 in accordance with UL 94⁶ or pass the needle flame test in accordance with DIN EN 60695-11-5.



Excerpt from IEC/DIN EN60335-1, test sequence for unsupervised appliances with rated current greater than 0.2 A

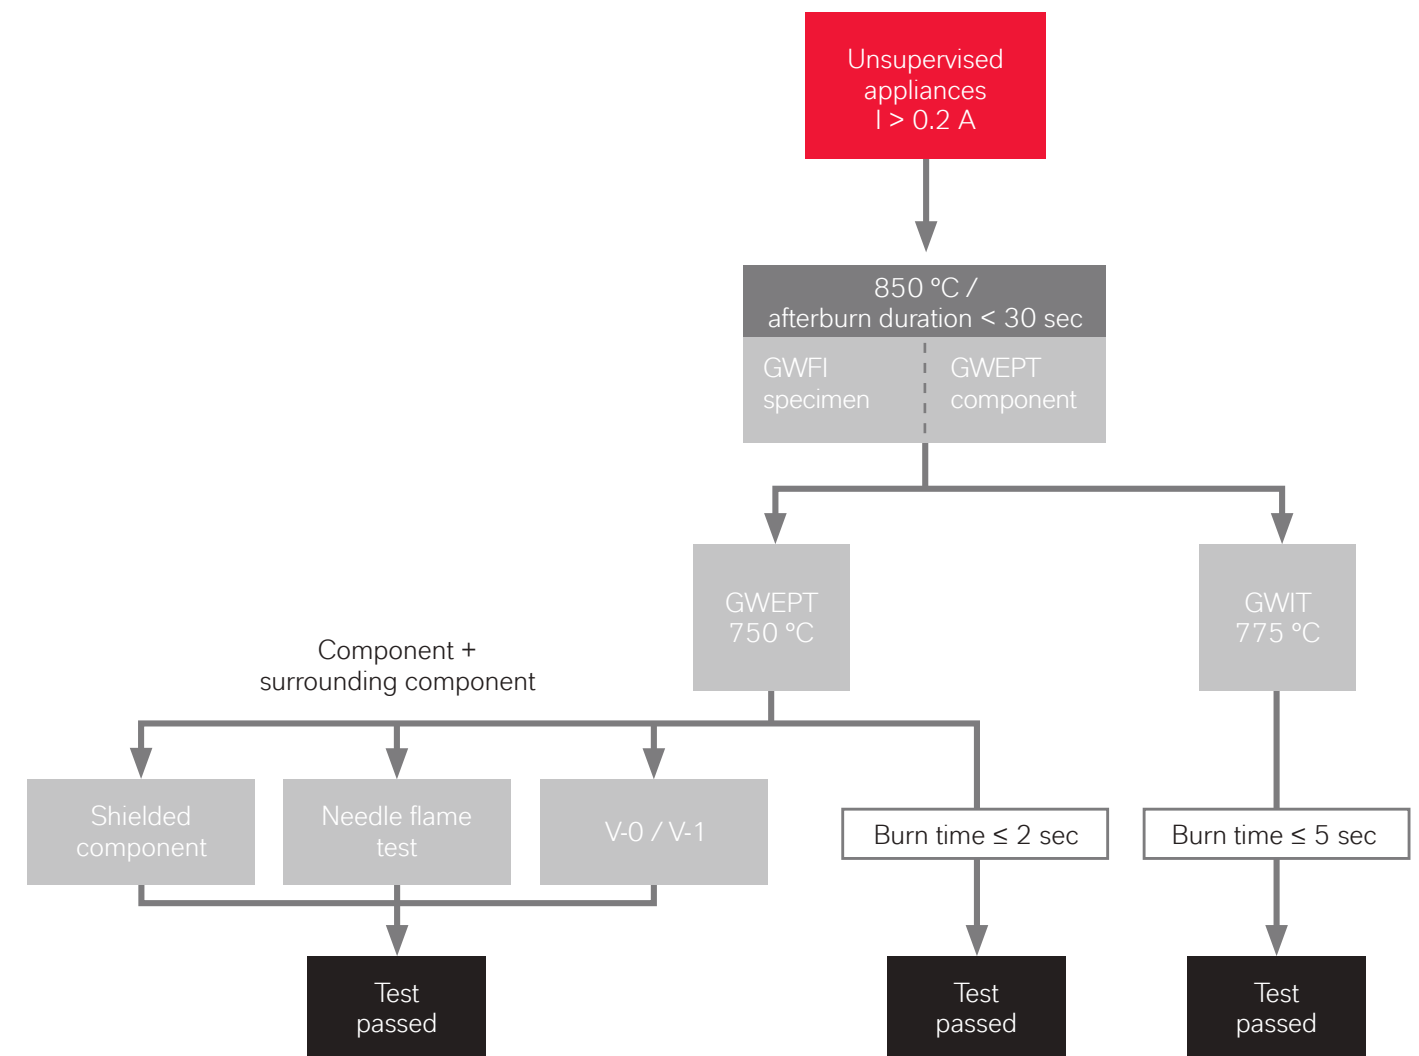

SELECTED APPLICATION-RELATED STANDARDS – AN OVERVIEW

EN 45545-1,-2^{7a,b} “Fire protection on railway vehicles”

This European Standard regulates, among other things, the requirements for fire safety where flammable materials and components are used in railway vehicles. It has been in effect since 2013 and will replace the national standards by not later than 2017. The requirements for E&E components are provided in the table “Requirements for listed components.” An “R” requirements set is assigned to the listed components. It includes a number of tests. Which tests must be carried out on the material and which limits must be complied with at which hazard level are listed in the table “Material requirements.” The hazard level depends on the rail vehicle design

and the type of rail transportation – referred to as the design and operation categories. This differentiation reflects the length of time the passengers spend in the rail vehicle during a fire and how much they are endangered as a result. A hazard level that classifies the potential risk is defined for each design category, based on the operation category. A total of three hazard levels (HL 1 – 3) are defined, with HL3 being the highest. The main tests for E&E components made of plastic serve to determine the maximum visible smoke production in accordance with EN ISO 5659-2⁸ and analyze gases in accordance with NF X70-100-1/-2⁹.

Requirements for listed components

Component No.	Name	Description	Requirement
E	Electronic equipment		
EL5	Components of the supply system – exterior	Surge arresters, insulators, switches, main switches	R23
EL6A	Supply line system components and high-voltage components – interior	Insulators, current and voltage transformers, main switches, contactors	R22
EL6B	Supply line system components and high-voltage components – exterior	Insulators, current and voltage transformers, main switches, contactors	R23
EL7A	Throttles and coils – interior	Throttle coils for filtering the supply line, windings for air-cooled transformers, including spacers and air deflectors	R22
EL7B	Throttles and coils – exterior	Throttle coils for filtering the supply line, windings for air-cooled transformers, including spacers and air deflectors and insulation of the traction motor winding	R23
EL10	Small electronic components	Examples include low-voltage circuit breakers, overvoltage relays, contactors, contact relays, switches, control or signal switches, connection points, fuses	R26

Material requirements

Requirements set (relevant component No.)	In regard to test method	Parameter and unit	Maximum or minimum	HL1	HL2	HL3
R22 (N16; EL2; EL6A, EL7A; M2)	T01 EN ISO 4589-2: OI	Oxygen content %	Minimum	28	28	32
	T10.03 EN ISO 5659-2: 25 kWm ²	D _s max. dimensionless	Maximum	600	300	150
	T12 NF X 70-100-1 and -2 600 °C	CIT _{NEP} dimensionless	Maximum	1.2	0.9	0.75
R23 (EX12; EL2; EL5 EL6B; EL7B; M3)	T01 EN ISO 4589-2: OI	Oxygen content %	Minimum	28	28	32
	T10.03 EN ISO 5659-2: 25 kWm ²	D _s max. dimensionless	Maximum	-	600	300
	T12 NF X 70-100-1 and -2 600 °C	CIT _{NEP} dimensionless	Maximum	-	1.8	1.5
R24	T01 EN ISO 4589-2: OI	Oxygen content %	Minimum	28	28	32
R26 (EL10)	T17 EN60695-11-10	Vertical small burner test	Minimum	V-0	V-0	V-0

SELECTED TEST METHODS – AN OVERVIEW

The test methods for plastics in E&E applications can be divided into several categories, and also into tests for evaluating:

- fire resistance
- electrical safety
- thermal stability and conductivity
- aging resistance and light stability

Flame retardance tests

The tests for the flame retardance of plastics are oriented to typical parameters of a fire, such as flammability, heat generation and flame propagation. In addition there are tests for safety-related secondary effects of fires, such as smoke production, burning drops of material, and corrosiveness and toxicity of combustion gases and solid fire residues. The most important flame retardance tests for E&E components are specified in the standards of the U.S.-based testing organization Underwriters Laboratories (UL) and the International Electrotechnical Commission (IEC).

Tests in accordance with UL 94 – “Tests for Flammability of Plastic Materials for Parts in Devices and Appliances”


The UL 94⁶ regulation specifies test methods for evaluating the flame retardance and fire safety of plastics. The tests correspond to the content of the tests in accordance with DIN IEC 60695-11-10 and -20⁵ and CSA C22.2¹⁰ (Canadian Standard Association). The tests evaluate the fire behavior of specimens.



UL 94 HB Test

The UL 94 HB test (see the graphic) provides information on the extent of the horizontal flame propagation. After test specimens have been stored for 48 hours at 23 °C and 50 percent relative humidity, flame from a Bunsen burner or Tirill burner is applied to them for 30 seconds. The test criterion is the burning rate. One difference compared to IEC 60695-11-10⁵ is the HB rating (see the graphic “Classification of the HB test according to IEC-60695-11-10”).

Test rig for UL 94 HB

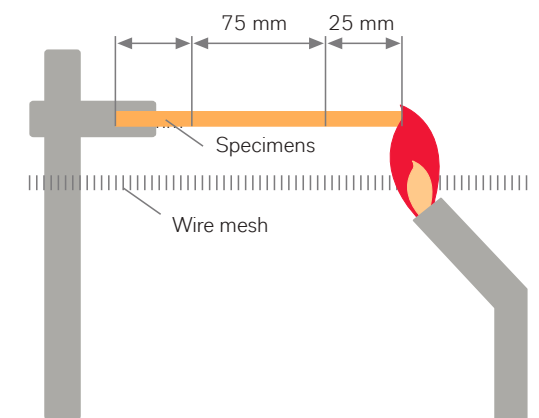

Test criterion	Burning rate	Classification
Thickness of specimen 3 – 13 mm	≤ 40 mm/min	HB
Thickness of specimen < 3 mm	≤ 75 mm/min	HB
Flame extinguished prior to first gauge mark	0 mm/min	HB

Classification of the HB test according to IEC-60695-11-10


Test criterion	Burning rate	Rating
Specimen thickness 3-13 mm	≤ 40 mm/min	HB40
Specimen thickness < 3 mm	≤ 75 mm/min	HB75
Flame turned off before first reference mark	0 mm/min	HB

SELECTED TEST METHODS – AN OVERVIEW

UL 94 V test

The UL 94 V test (see the graphic) measures the vertical flame propagation and droplet behavior of the specimen. The specimen is conditioned for two days at 23 °C and 50 percent relative humidity and then for seven days at 70 °C in a hot-air oven. After that, it is supported vertically and a 20-mm-long Tirill burner flame is applied to its lower end for 10 seconds. The burner is removed and the self-extinguishing time of the flame on the specimen is measured. Immediately after that, a flame is applied to the specimen for an additional 10 seconds and the burn duration and glow duration are measured once again. Any ignition of a surgical cotton patch placed below the sample (caused by burning droplets) is evaluated. Depending on the result, a classification is assigned in the Flammability Classes V-0, V-1 or V-2.

Test rig for UL 94 V

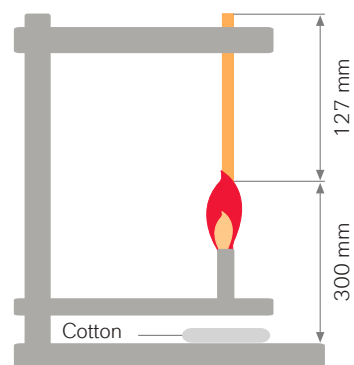


	V-0	V-1	V-2
Burning time following each flame application	≤ 10 s	≤ 30 s	≤ 30 s
Total burning time per set (10 flame applications)	≤ 50 s	≤ 250 s	≤ 250 s
Burning down to clamp	no	no	no
Burning/glow time following 2 nd flame application	≤ 30 s	≤ 60 s	≤ 60 s
Ignition of the cotton	no	no	yes

UL 94-5V test

The UL 94-5V test (see the graphic) can be carried out on specimens that have already been classified as V-1 or better in accordance with the UL 94 V test. First, a flame is applied to the vertically aligned specimen 5 times, for 5 seconds each time, and at 5-second intervals. The flame height is 125 mm. If this test is passed, a second test is carried out on a fixed horizontal test plate under the same conditions. If this leads to hole formation in the plate, the test is passed with the classification 5VB. If there is no hole formation, the specimen is classified 5VA.

Test rig for UL 94-5V

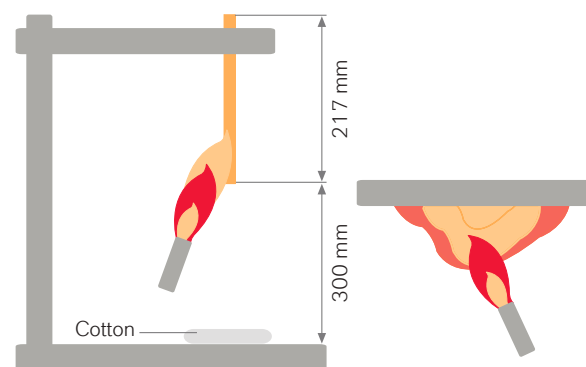

	5VA	5VB
Total burning time after 5 th flame application	≤ 60 s	≤ 60 s
Ignition of the cotton	no	no
Formation of holes on plaque	no	yes

Glow-wire tests in accordance with IEC 60695-2-11 to -13


These tests in accordance with IEC 60695-2-11 to -13^{4a,b,c} assess the ignition properties of specimens that contact a heated glowing wire, and their afterburn behavior.

With the GWIT test (Glow Wire Ignition Temperature) in accordance with IEC 60695-2-13^{4c}, the glow wire is applied to specimens in 50 °C increments from 500 to 900 °C, and at 960 °C, for periods of 30 seconds. Ignition is defined as the occurrence of flames for longer than 5 seconds. The GWIT value is expressed as the temperature 25 °C higher than the temperature at which no ignition of the specimen has been observed. It is not acceptable for burning droplets to fall from the specimen.

With the GWFI test (Glow Wire Flammability Index) in accordance with IEC 60695-2-12^{4b}, the glow wire is applied to specimens in 50 °C increments from 500 to 900 °C, and at 960 °C, for periods of 30 seconds. It is acceptable for the specimen to ignite, but it must self-extinguish within a testing and observation duration of 60 seconds. It is not acceptable for burning droplets to fall from the specimen. The GWFI value is the maximum glow-wire temperature at which the evaluation criteria are fulfilled.

The GWEPT test (Glow Wire End Product Test) in accordance with IEC 60695-2-11^{4a} corresponds to the GWFI test, however it is carried out on the finished part.

Test rig for the Glow Wire test

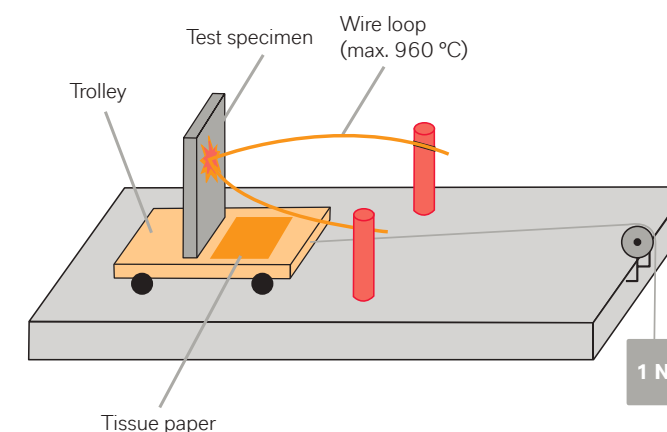


Application time: 30 sec.

Lowest Oxygen Index-Test (LOI)

The Lowest Oxygen Index test (oxygen index, see the graphic) is described in the standards ISO 4589-1¹¹ and ASTM D 2863 A¹² (American Society for Testing and Materials). It specifies the minimum concentration of oxygen in an oxygen/nitrogen mixture that will support a specimen burning continuously and independently. The LOI value is not listed on the UL Yellow Card and can be found only on the data sheet of the plastic manufacturer.

Lowest Oxygen Index-Test (LOI)

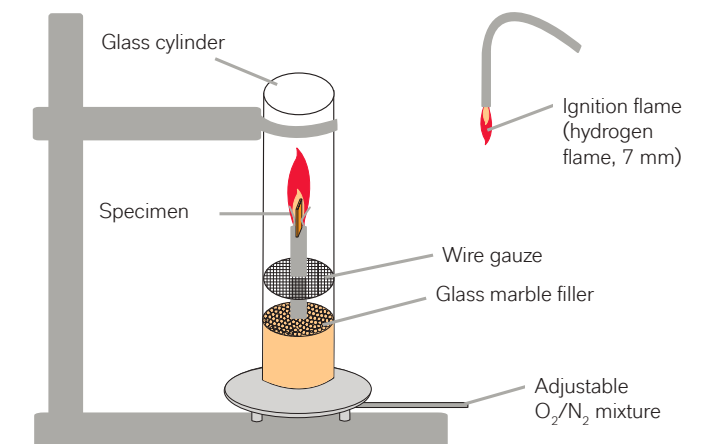

SELECTED TEST METHODS – AN OVERVIEW


Needle flame test

The needle flame test in accordance with IEC 60695-11-5¹³ (see the graphic) is carried out on the finished part. It recreates the effects of a small flame that could arise due to a malfunction in an electrical device or appliance. This is done by directing a 12-mm-long test flame onto the specimen, generally for 5, 10, 20, 30, 60 or 120 seconds. The test determines the burned distance and afterburn duration. Unless specified otherwise, the needle flame test is passed when

- the specimen does not ignite
- the burn duration is under 30 seconds
- droplets of material or falling, burning particles self-extinguish sufficiently to prevent tissue paper underneath from igniting

For special requirements, the test conditions can be varied and/or made more demanding.

Needle flame test

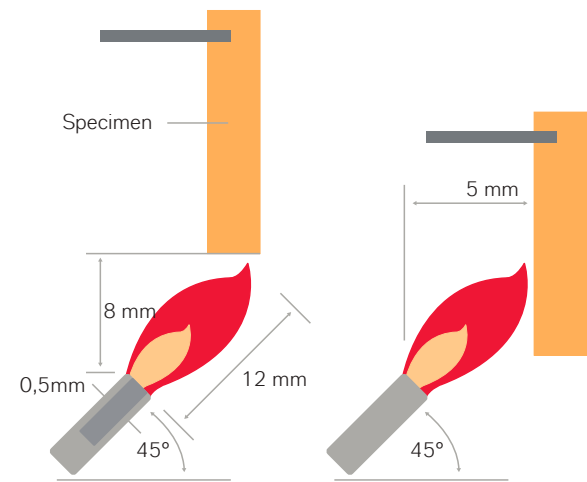


Examples of testing positions

Hot Wire Ignition-Test (HWI)

The HWI test in accordance with ASTM D 3874 and IEC 60695-2-20 (see the graphic) simulates a situation where live parts (e.g. wires) are heated through direct contact with the specimen as the result of overload. Resistance wire is wound five times around the specimens at intervals of 6.4 mm. The wire is brought to red heat (approx. 800 °C) using approx. 10 V and 65 watts. The test determines the time (measured in seconds) needed to ignite the specimen. Depending on the ignition time, the specimen is classified in the flammability categories PLC 0 to 5 (Performance Level Categories), in accordance with UL 746A.

Hot Wire Ignition-Test (HWI)

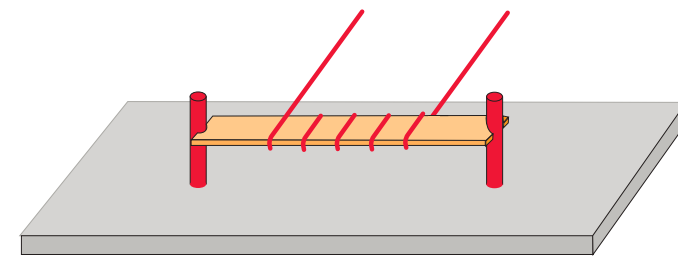


Time in seconds to ignition	PLC assigned
120 ≤ IT	0
60 ≤ IT < 120	1
30 ≤ IT < 60	2
15 ≤ IT < 30	3
7 ≤ IT < 15	4
0 ≤ IT < 7	5

High Amp Arc Ignition Test (HAI)

The HAI test in accordance with UL 746A¹⁴ (see the graphic) simulates the ignition of plastics through application of electrical arcing. The specimen is positioned between two electrodes and subjected to high-current arcs at regular time intervals. The evaluation criterion is the number of arc exposures required to ignite the specimen. Depending on the number, the specimen is classified in the categories PLC 0 to 4.

High Amp Arc Ignition Test (HAI)

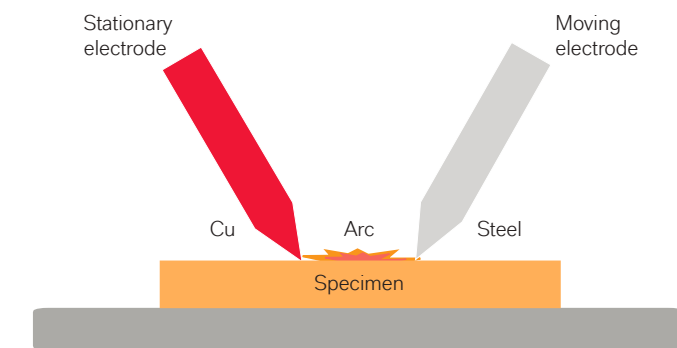


Number of arcs (NA) required for ignition	PLC assigned
120 ≤ NA	0
60 ≤ NA < 120	1
30 ≤ NA < 60	2
15 ≤ NA < 30	3
0 ≤ NA < 15	4

Tests of electrical behavior

Comparative Tracking Index A (CTI A)

The CTI A test in accordance with UL 746A¹⁴ and/or IEC 60112¹⁵ measures the voltage which causes tracking paths. This is done by allowing successive drops of a standard electrolyte testing solution to fall on a specimen placed between two live electrodes (see the graphic). The CTI A is the highest voltage value at which there is no failure after 50 drops have fallen on each of five specimens. In accordance with UL 746A¹⁴, a corresponding, dimensionless PLC classification is assigned to this value. The test sequences in accordance with UL 746A¹⁴ and IEC 60112¹⁵ are comparable, however there are differences in the selection of electrolytes and the assessment of the individual tests. Furthermore, the result is directly specified as the value of the voltage withstood by the specimen.

Comparative Tracking Index

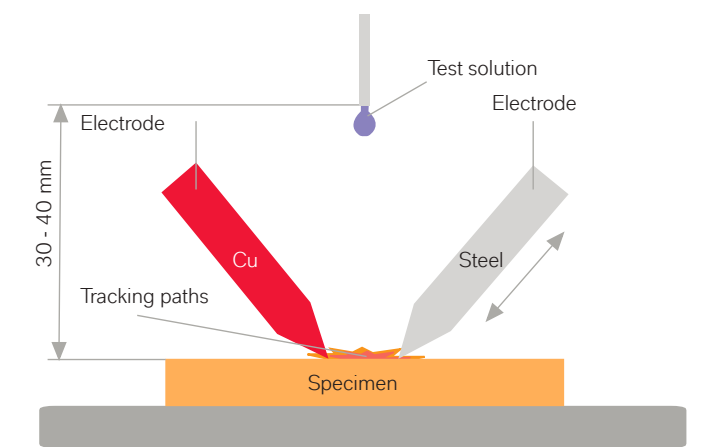

CTI range Tracking Index (TI) in V	PLC assigned
600 ≤ TI	0
400 ≤ TI < 600	1
250 ≤ TI < 400	2
175 ≤ TI < 250	3
100 ≤ TI < 175	4
0 ≤ TI < 100	5

SELECTED TEST METHODS – AN OVERVIEW


Comparative Tracking Index M (CTI M)

The CTI M test (IEC 60112¹⁵) is a CTI test version made more stringent than the CTI A test. It also uses a wetting solution that is standardized, but with double the electrical conductivity compared to the CTI A version. A value of CTI-M 300, for example, means that 50 drops of Solution B at less than 300 volts do not cause any leakage current.

High-voltage tracking resistance

The test for high-voltage tracking resistance in accordance with DIN EN 60587 and ASTM D230¹⁶ (see the graphic) recreates how strongly the insulating capacity of a surface changes at higher voltages outdoors when subjected to moisture and soiling. According to UL 746A¹⁴ the testing begins with a test voltage of 1 kilovolt. A specimen is considered to have passed the test if the time-to-track is greater than 60 minutes. If this is the case, the test voltage is increased by 0.5 kilovolt and the test is repeated. The test result is the maximum test voltage at which the time-to-track of 60 minutes is reached with each of five samples. This Inclined-Plane Tracking test (IPT) is entered on the UL Yellow Card.


Inclined Plane Tracking-Test

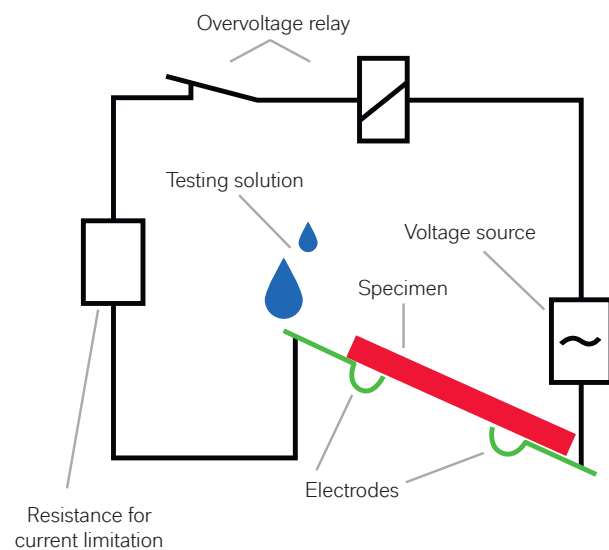

High Voltage Arc Tracking Rate-Test (HVTR)

The HVTR test (high-voltage tracking rate) in accordance with UL 746A¹⁴ examines the formation and spread of tracking distances on the surface of plastic specimens. Its set-up corresponds to that of the HAI test. High-voltage arcs are ignited on the surface of the specimen for two minutes (see the graphic). The electrodes are moved apart from each other until the arc extinguishes, and then moved closer to each other again once it has extinguished. After the two minutes, the length of the resulting tracking distance is measured and divided by 2. The test result is the rate of speed in mm/min with which a conductive tracking distance forms on the specimen through high voltage. Depending on the rate of speed, the specimen is classified in the categories PLC 0 to 4 in accordance with UL 746A¹⁴.

Test rig for HVTR

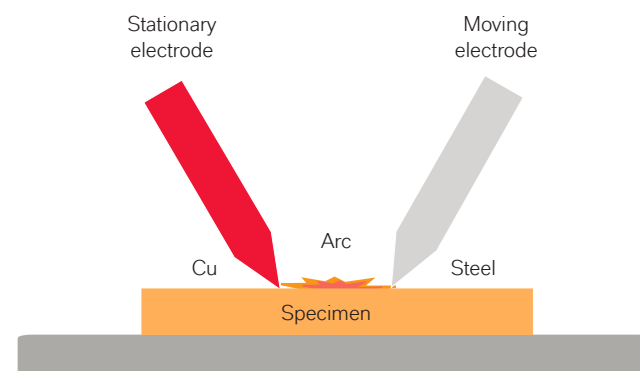


High Voltage Arc Tracking Rate in mm/min	PLC assigned
0 < TR ≤ 10	0
10 < TR ≤ 25	1
25 < TR ≤ 80	2
80 < TR ≤ 150	3
150 < TR	4

Arc resistance

The test of arc resistance in accordance with ASTM D495¹⁷ (see the graphic) investigates the ability of insulating materials to resist an arc at a high voltage but with a weak current in the vicinity of the insulating surface. The purpose of the test is to make a relative distinction between solid electrical insulating materials. A specimen is subjected to a test voltage of 12,500 volts until it ignites, a hole forms, or a conductive tracking path forms. The time it takes for a failure criterion to occur is measured in seconds. Depending on this result, the specimen is classified in the categories PLC 0 to 7 in accordance with UL 746A¹⁴.

Test rig for Arc Resistance test

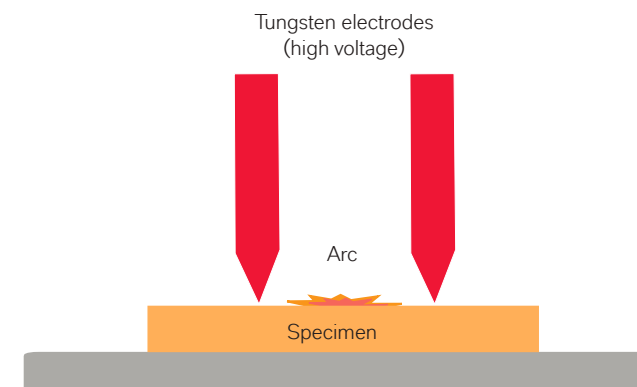


Arc Resistance in seconds	PLC assigned
≥ 420	0
360 – 419	1
300 – 359	2
240 – 299	3
180 – 239	4
120 – 179	5
60 – 119	6
≤ 59	7

Dielectric strength

The dielectric strength in accordance with IEC 60243-1¹⁸ and ASTM D149A provides information on the strength of an insulating material in terms of its ability to withstand high voltage. This corresponds to the electric field strength at which the conductivity of an insulator abruptly increases. The voltage is determined (see the graphic) just before the breakdown. The surrounding medium can be air or oil. Because the breakdown voltage depends on the thickness of the specimen, it is divided by this thickness value. The unit of dielectric strength is therefore expressed in kV/mm.

Dielectric strength

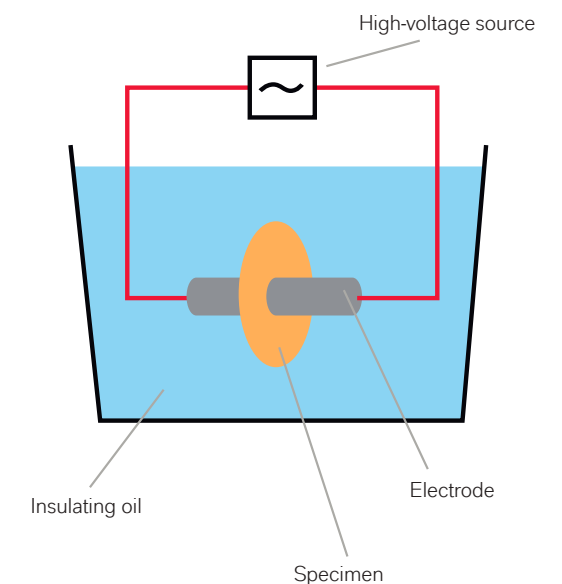


SELECTED TEST METHODS – AN OVERVIEW

Surface resistivity

Surface resistivity is a measure of the strength of current that flows along the surface of an insulating material when voltage is applied to the material and it is in contact with an electrical conductor. It is measured (IEC 60093¹⁹, ASTM D257) by attaching electrodes with standardized dimensions to the surface of a specimen at a defined distance and applying direct current (see the graphic). The surface resistivity corresponds to the ratio of the applied voltage to the current between the electrodes. It is expressed in ohms.


Surface resistivity

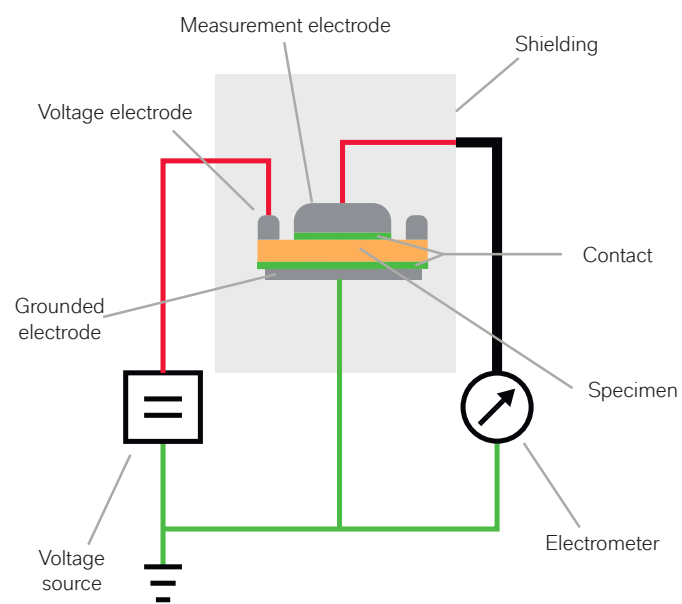

Volume resistivity

When a voltage is applied to an insulating material, a current flows; and the current strength depends on the resistance of the insulator. This resistivity (IEC 60093¹⁹, ASTM D257) is determined by using two electrodes to apply a defined voltage to surfaces of a specimen positioned opposite to each other (see the graphic). The volume resistivity is determined on the basis of the measured resistance, which is multiplied by the value for the measured surface and divided by the specimen length. It is expressed in $\text{ohm}\cdot\text{m}$. The current along the specimen surface (surface resistivity) is not taken into account.

Volume resistivity

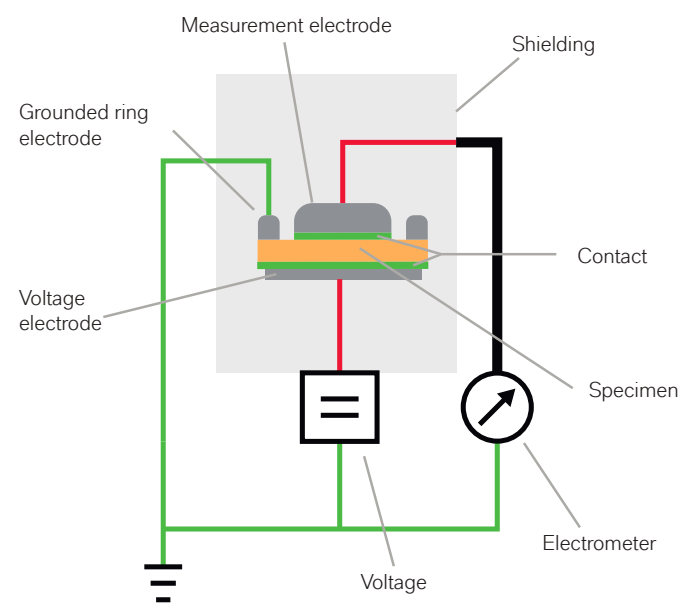

Relative permittivity

An insulating material's relative permittivity (formerly referred to as the "dielectric constant") is a dimensionless quantity. It indicates the extent to which an insulating material affects the capacity of a capacitor. Relative permittivity is the ratio of the capacitance of a capacitor using that material as a dielectric, compared to a similar capacitor that has vacuum as its dielectric. The better the material's electrical insulation, the lower the relative permittivity. If a plastic used in AC applications has a low relative permittivity, its molecule fragments will be less susceptible to dipole oscillations. These dipole oscillations, in turn, result in energy losses and/or heat in the plastic, which in electronic components can cause damage or malfunctions.

Dielectric loss factor

The dielectric loss factor indicates how much energy an insulation material absorbs in an alternating electrical field and converts into heat loss. In an optimal dielectricum, voltage waveform and current waveform are exactly 90° out of phase. Depending on the insulation material, however, heat losses occur to varying degrees, which is why the current waveform lags behind the voltage waveform. As a result, the phase shift between the current waveform and the voltage waveform becomes less than 90°. The height of this divergence is referred to as the dielectric loss angle. And the tangent of this loss angle is defined as the dielectric loss factor. The smaller the loss factor, the better the dielectric properties of a material. Plastics with a high loss factor are not suitable as insulation materials for high-frequency applications. But they are quite suitable for being joined by means of high-frequency welding, because they quickly become fused through the high heat loss. Relative permittivity and loss factor are measured with the same devices (IEC 60250²⁰, ASTM D150).



SELECTED TEST METHODS – AN OVERVIEW

Tests of long-term thermal resistance


Relative Temperature Index (RTI)

The RTI in accordance with UL 746B²¹ is a measure of the thermal aging resistance of plastics at high temperatures. It enables conclusions about the maximum service temperature at which a material can still retain key properties within reasonable limits – over long periods and despite the effects of aging. The aging is normally determined in relation to a reference material. The tests determine the temperature at which the observed property has diminished to 50 percent of its initial value after heat aging (see the graphic).

THE FOLLOWING ARE RTIS DEFINED FOR SPECIFIC PROPERTIES:

- **RTI Elec (electrical load):**
dielectric strength
- **RTI Str (mechanical load without impact):**
preferably tensile strength, otherwise flexural strength
- **RTI Imp (mechanical load with impact):**
primarily critical impact resistance, in some cases also other tests, e.g. impact strength

Relative Temperature Index (RTI)

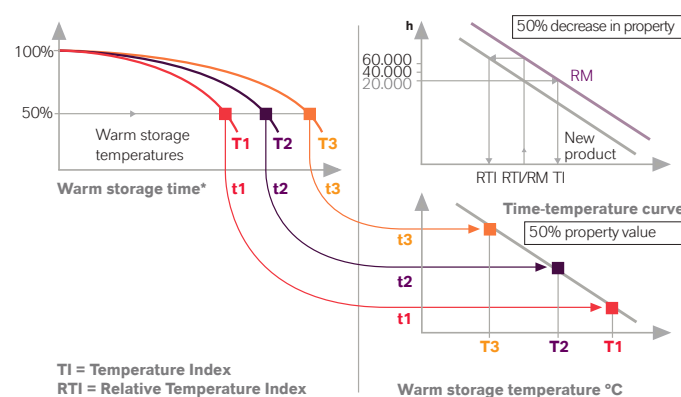

Temperature Index (TI)

The TIs in accordance with IEC 60216-1²² are a measure of the continuous service temperature at which critical properties of a material (electrical insulation, strength, toughness) still remain within an acceptable range (50 percent criterion after 5,000 or 20,000 hours) despite aging.


Determining thermal conductivity and diffusivity

The principles of methods for determining thermal conductivity and diffusivity of plastics are described in standards including DIN EN ISO 22007²³. There are stationary methods that subject a specimen to an uninterrupted flow of heat, and also transient measurement techniques that examine the chronological sequence of a heat flow. The specimens also vary depending on the specific method used. Practical experience has shown that when different methods are used, it is difficult to compare certain resulting thermal conductivity properties. Furthermore, the measurement of a specimen's thermal conductivity provides only qualitative findings regarding the thermal conductivity of the component for which the material may be intended.

Hot disk method

With the hot disk method (also known as the hot wire method), a heating element with temperature sensors is placed between two identical specimens to observe the spatial and chronological diffusion of a heat pulse. The flow of heat penetrates uniformly in all spatial directions. Therefore the calculation of the thermal conductivity results in an integral value. The method offers the advantage that it is not only quick and easy to use, but also suitable for many geometries. The specimen geometry has not been standardized.

Hot wire method ("hot disk")

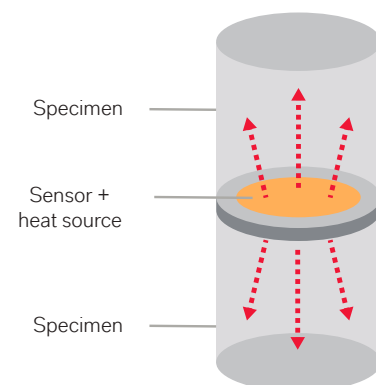


Heat flow in 3 directions
→ integral value

Laser flash method

The laser flash method allows directional measurement of thermal conductivity. A specimen is placed between a flash lamp (the heat source) and an infrared detector. After discharge of an energy pulse (usually a xenon flash lamp), the temperature increase on the facing side of the specimen is monitored and the directional thermal diffusivity is determined. Once the heat capacity has been measured against a reference, this measurement serves as the basis for calculating the thermal conductivity. Preparation of the specimen for the laser flash method can entail high costs.

Laser flash method

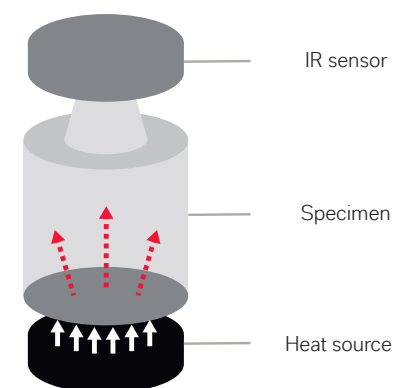

Heat flow in 1 direction
→ directional value

Determining reflectivity

Reflectivity (also called "reflectance" and "degree of reflection") indicates what percentage of light that falls on an object is reflected. This involves differentiating between specular reflection, diffuse reflection, and the mixed reflection made up of both of these proportions. The reflectivity depends on the wavelength. As a rule, it is determined photometrically in accordance with DIN 503624, e.g. with a sphere-type spectrophotometer. By means of numerical gloss control, the measurement data can be recorded either including gloss or excluding gloss. In addition to the L*a*b* color space,

the reflection of the incident light can be determined wavelength-dependent. The proportion of the reflected light on the surface of the plastic also enables conclusions about the absorption behavior of the surface. A particularly important factor here is the high-energy UV component of the light. It can lead to degradation of the polymer matrix, resulting in aging (yellowing) of the plastic. This must be taken into account with plastics for reflectors of LED lamps, for example.



FLAME RETARDANTS AND FIRE PROTECTION – AN OVERVIEW

In Polyamide 6, polyamide 66 and PBT are frequently used in the electrical and electronics industry to insulate live parts. To ensure fire safety, in most cases this means they are required to contain flame retardants, which have the property of being able to reduce the flammability of materials and the speed of flame propagation. Most are based on chemical substances that contain the elements bromine, chlorine, phosphorus and nitrogen, and are compounded with the polymer matrix. Their modes of action, advantages and disadvantages are very varied, so in this section we present the most important flame retardants for polyamide 6, polyamide 66 and PBT.

Halogenated flame retardants Area of effect 1 (see the graphic)

Bromine and chlorine are present in these flame retardants as organic halogen compounds. Halogen radicals are produced in a fire, and they intercept the energy-rich hydrogen and hydroxyl radicals in the flame, extracting its energy. Advantages of halogenated flame retardants are their efficient flame retardance and good compounding properties. A disadvantage is that they produce toxic and corrosive gases in a fire. They are therefore less suitable for applications that require low toxicity of smoke gases.

Phosphorous-based flame retardants Area of effect 4 (see the graphic)

Phosphorous is compounded in the plastic either as inorganic red phosphorus or as an organic phosphorus compound. In a fire, organic phosphorus compounds produce phosphorus oxides, which remove water from the substrate, thus charring the polymer matrix. The carbon char layer separates the flame from the polymer, taking away its "nourishment." Red phosphorus has a similar effect. Organic phosphorus compounds are often used together with nitrogen-based sub-

stances that cause a foaming of the matrix (intumescence), which impedes the ingress of oxygen and heat. In addition, phosphorus acts as a radical scavenger in the gas phase, like halogenated flame retardants. Processing of red phosphorus can produce corrosive gases. And its inherent color limits its use to dark-colored applications. Organic phosphorus compounds are significantly less corrosive and do not restrict coloring options, but the processing window of the plastics compounded with it is smaller.

Inorganic flame retardants Area of effect 3 (see the graphic)

Inorganic flame retardants such as magnesium hydroxide (MDH) split off water when consuming energy. As a result, the matrix cools and the combustion gases are diluted with water. They display very minimal secondary effects of fire, such as smoke gas toxicity and smoke gas density, however they influence the mechanical and rheological properties of the compounds.


Nitrogen-based flame retardants Areas of effect 2, 3 and 5 (see the graphic)

Nitrogen-based flame retardants produce their effect by means of various mechanisms. They decompose when subjected to heat, for instance, which serves to draw off energy from the flame area. And gases are produced that allow foaming of the matrix, which impedes the ingress of oxygen and heat. If the flame retardant also contains phosphorus, a flame-inhibiting carbon char layer forms. Furthermore, a matrix depolymerization can occur, so that the matrix draws away from the heat source. Nitrogen-based flame retardants are less effective in reinforced compounds, but they are easy to process in most cases.



Mode of action of flame retardants

The diagram shows in summary form, how and where flame retardants act.

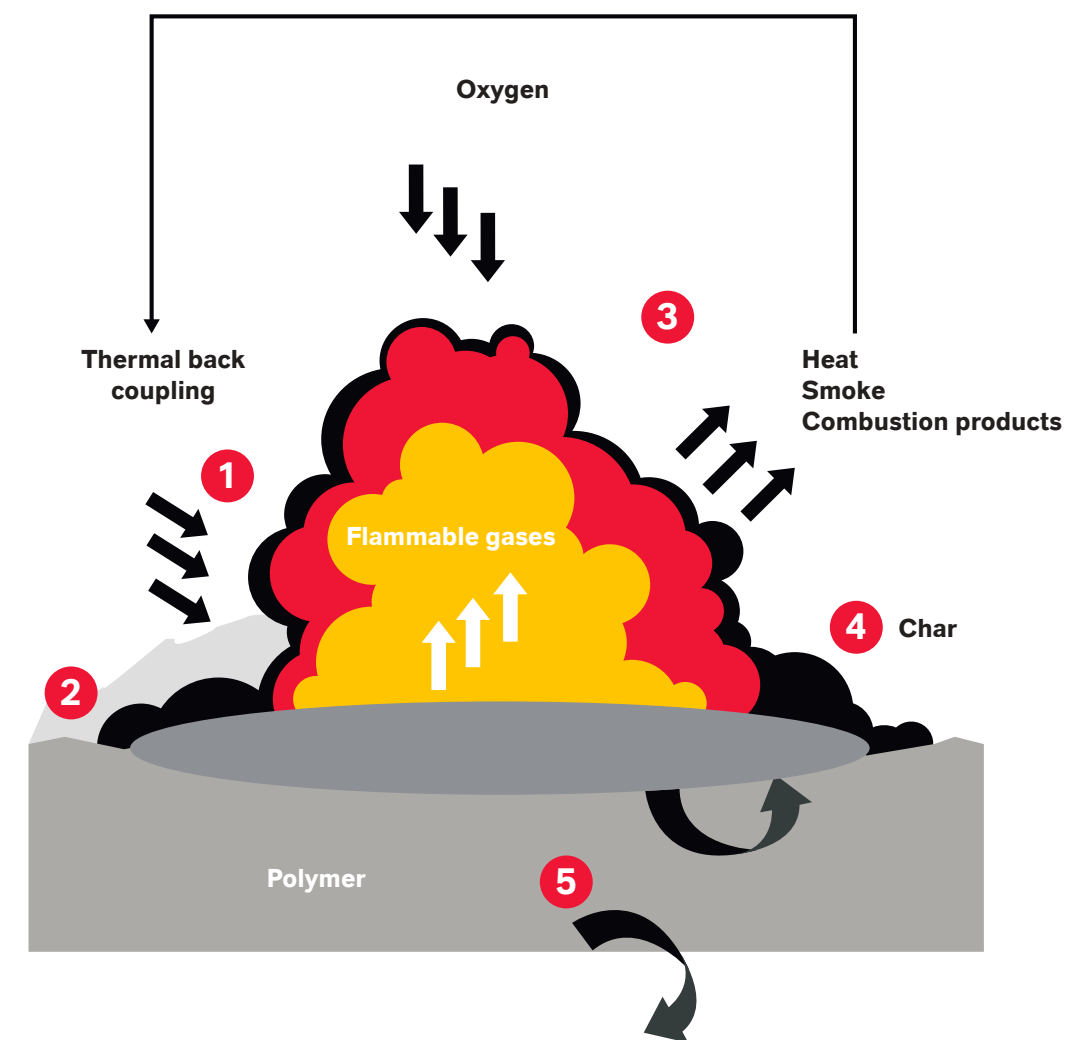

- 1 Radical recombination**
Halogenated FR additives
- 2 Intumescence**
Foam produced by intumescence system (blowing agent)
- 3 Fire inhibiting gases**
Decomposition of water from minerals as $Mg(OH)_2$
Decomposition of N_2/NH_3 from melamine cyanurate
- 4 Surface passivation**
Char formation by phosphoric acid or red phosphorus
- 5 Matrix depolymerisation**
Depolymerisation induced by FR system

OUR THERMOPLASTICS

Our range of plastics covers a very wide spectrum of properties. It encompasses polyamide 6 and polyamide 66 compounds of the **Durethan®** brand, PBT compounds of the **Pocan®** brand, and compounds based on polycyclohexylene dimethylene terephthalate (PCT).

The fundamental strengths of the **Durethan®** polyamides include not only their excellent mechanical strength and stiffness, but also good electrical insulation properties, high resistance to heat and chemicals, low friction, good emergency running properties, wear resistance and very good attenuation of noise and vibration.

Pocan® is very heat-resistant, absorbs very little moisture, and displays good electrical insulation properties, outstanding strength and hardness, and excellent slip properties. In addition it features good resistance to chemicals, impressive abrasion resistance and low susceptibility to stress cracking.

The properties of the PCT-based compounds are similar to those of Pocan but considerably more heat-resistant.

The product range for the E&E industry

Our portfolio of compounds for the E&E industry covers a broad spectrum. It also features numerous flame-retardant material variants distinguished by superior flame retardance, good electrical values, excellent flowability, and very good mechanical properties.

All of our products are in compliance with the EU directives WEEE (Waste Electrical and Electronic Equipment) and RoHS (Restriction of the Use of certain Hazardous Substances in Electrical and Electronic Equipment), as well as the European Union's REACH regulation (Registration, Evaluation and Authorisation of Chemicals, VO (EG) No. 1907/2006). Most of the flame-retardant materials fulfill the fire protection requirements and/or glow-wire tests (GWIT, GWFI) of the household appliances standard IEC 60335-1³.

Our range for injection molding and extrusion of E&E components includes:

- non-reinforced compounds and fiber-, mineral- and/or glass-bead-reinforced compounds
- products with halogenated or halogen-free flame-retardant packages
- flame-retardant materials that produce very little smoke in the event of fire
- products with outstanding flowability
- highly reinforced materials for very strong and stiff components
- materials with low susceptibility to corrosion
- materials with excellent color stability in hot-air aging tests

Examples of the latest developments include:

- compounds with high resistance to LED light
- light-stable and lead-free polyester suitable for vapor phase soldering, with excellent light reflection
- materials with excellent thermal conductivity
- polyamides with extraordinary temperature stability
- product grades that are flame-retardant but also display very low warpage and are heat-resistant and weather-resistant
- laser-transparent configurations for laser radiation welding



Selected innovative materials

In this section we present a selection of the latest innovative materials that underscore our expertise as a partner of the E&E industry.


PCT compounds: good light reflection, light-stable and lead-free, suitable for vapor phase soldering

We are offering four new PCT compounds specially developed for housings and sockets of LED chips, in mineral-reinforced and/or glass-fiber-reinforced variants. Their light reflection is very high, ranging from 93 percent to nearly 96 percent (450 nm). Used as a material for LED housings, they reflect the light of the LEDs almost completely, keeping brightness losses to a minimum. Their good reflection behavior is retained to a great degree over time under LED use conditions. That is in contrast to high-melting polyamides, for example, which yellow from exposure to heat and light, causing their light reflection and thus the brightness of the LEDs to diminish noticeably.

- The properties of the four new PCT compounds are tailored for use in housings, sockets and other LED chip components. As a material for housings they reflect the LED light almost completely, so there are hardly any brightness losses.



LED chip material after hot storage at 120 °C

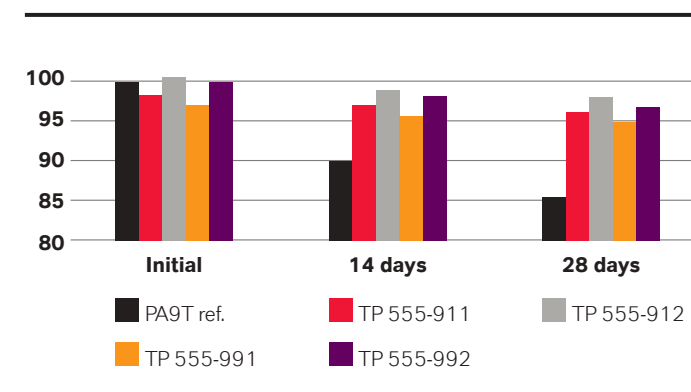

- Even after 28 days in storage at 120 °C, the light reflection of Pocan TP 555-911, -991, -912 and -992 is still far above 90 percent. In contrast, the reflection of high-melting polyamides diminishes noticeably, because they yellow with age.

OUR THERMOPLASTICS

Pocan® AF 4110:

Extremely low warpage, excellent flame retardance and color stability

Reinforced with a glass fiber content of 12 percent, the flame-retardant blend of PBT and ASA (acrylic ester-styrene-acrylonitrile) displays extremely low warpage and excellent flame retardance. Subjected to tests in accordance with UL 94, it attained the best classification V-0 (0.4 mm). It results in good surfaces that are very low in emissions (VDA 278). Due to its excellent resistance to light and moisture, in applications it fulfills weathering tests in accordance with ISO 4892-3. This eliminates any need for the components to have separate, costly UV protective coatings. Like its "siblings" with 20 or 30 percent glass fiber content, the material is suitable for applications including battery cell housings, plug connectors that are subject to mechanical loads, and large, geometrically complex housings for electronic circuits such as battery management systems.

Durethan® BG 30 XXF, H2.0 XF und H3.0 XF:

Minimal warpage, excellent flowability

The three polyamide 6 compounds are reinforced with a 30 percent mix of glass fibers and glass microbeads. Their strong points include not only outstanding flowability, but also exceptionally low susceptibility to warpage. Featuring a good mechanical property profile, their flowability is more than 30 percent higher than that of Durethan® BG 30 X, a similar standard polyamide 6. The compound with H3.0 thermostabilization has very low copper and halide content and is customized for natural-colored and light-colored applications in electrical engineering and electronics, such as plugs, plug connectors and fuse boxes. The H2.0 material version is intended for components that are colored black and subjected to higher heat loads.

Pocan® B 1205 XF:

Tailored for miniaturization

Our wide range of easy-flowing Pocan® XF polyester compounds includes both reinforced and non-reinforced grades such as Pocan® B 1205 XF. Thanks to its outstanding flowability, this material is perfect for the trend toward miniaturization in the electrical and electronics industry. It is ideal for complex components with extremely thin wall thicknesses, such as mini-plugs. Compared to similar standard grades, the compound is more resistant to hydrolysis and exhibits a lower density, which means processors can save on material.

Pocan® BF 4232 HR:

Hydrolysis-stable and flame-retardant

Reinforced with a 30 percent glass fiber content, the PBT is a new product for safety-related E&E components that must remain functional in a hot and moist environment. Along with excellent hydrolysis stability, it displays outstanding flame retardance and passes the UL 94 test with the best classification of V-0 (0.4 mm). It achieves this excellent classification in all colors required for the test, which is the exception rather than the rule for materials of this type.

Durethan® BKV 25 FN27:

Material of choice for circuit breakers

This halogen-free, flame-retardant polyamide 6 is an alternative to mineral-filled halogen-free polyamide 6 grades for use in production of circuit breakers for low-voltage applications. The glass-fiber-reinforced material offers high mechanical strength and thermal stability. Components made of it can well withstand the enormous mechanical stresses and high temperature peaks that occur during a short circuit. It also meets the requirements for circuit breakers in higher performance classes (rated currents). The compound is classified in accordance with UL 94 V-2 (0.75 mm), and it achieved the best possible GWFI (Glow Wire Flammability Index) value for plastics (960 °C) for a component with wall thicknesses of less than 1 mm. The excellent heat resistance is confirmed by an HDT A value (ISO 75-1,-2) of 155 °C.

Durethan® XTS3:

Long-term resistance up to 200 °C

With XTS3 (Xtreme Temperature Stabilization) we have developed another high-tech heat stabilizing system for Durethan®. Like the XTS1 system already launched on the market, it raises the continuous service temperatures that polyamides 6 and 66 can withstand by around 60 °C, to approximately 200 °C. The heat stabilization is based not on an inorganic additive system, but on an organic one instead. And Durethan® material variants that feature this stabilizer system are particularly suitable for plastic parts that are subjected to high thermal loads and come into direct contact with metal components. That's because the metal- and salt-free stabilization ensures there is no contact corrosion. Possible applications in the E&E sector are housing parts, plug connectors and plug strips.

Pocan® BFN:

Comparable to halogenated PBT compounds

Reinforced PBT compounds with halogen-free flame retardance are in demand for reasons including ecological concerns. With this in mind, we have expanded our Pocan® PBT family to include new material variants that feature glass-fiber reinforcement contents of 13 percent, 20 percent and 25 percent, as well as organic phosphorus flame retardant packages. The compounds are as easy to process in a broad process window as comparable halogen-containing products and are also at least equivalent in terms of flame retardance, heat stability and shrinkage. And they offer very significant advantages with regard to tracking resistance, laser marking, color stability and density. The tracking resistance of Pocan® BFN 4231, for example, achieves a CTI A value (UL 746A-14) of 600 V (PLC 0 on the UL Yellow Card). Because the flame retardant package

is free of red phosphorus, Pocan® BFN is not susceptible to corrosion when in contact with metals.



High-modulus thermoplastics: Replacing metal

Manufacturers of household appliances, in particular, are increasingly trying to replace metal with thermoplastics. This is because thermoplastics offer advantages including greater design freedom and the possibility of cost-saving integration of functions by means of injection molding. Here, we offer a wide range of polyamide and PBT compounds with glass fiber content as high as 60 percent, which are outstanding in terms of their good melt flow rates and excellent levels of strength and stiffness. Polyamide 6 and polyamide 66 variants in the Durethan® range that are reinforced with a glass fiber content of 60 percent, for example, achieve tensile modulus values of over 13,000 MPa (conditioned).




HIANT® – CUSTOM SERVICES FOR THE E&E INDUSTRY

The goal of our HiAnt® services is to collaborate with customers around the world on the development of intelligent and innovative system solutions in the areas of materials, applications, processing methods and technologies. HiAnt® spans the entire development chain of a component. Examples of selected services relevant for the E&E industry include:

- experiments on corrosion behavior of flame retardant additives upon contact with metals
- standards-compliant performance of important flame retardance tests
- provision of angle-resolved BRDF data (Bidirectional Reflectance Distribution Function) for projects
- Technical Service Center facilities for experiments with laser marking in a wide variety of colors

- Technical Service Center facilities for joining experiments using ultrasonic, vibration and IR welding, for optimizing production processes and materials
- filling analyses for purposes including the positioning of sprues and detecting weld lines and air pockets
- calculations related to warping and to design of the tool cooling system
- in the case of materials displaying anisotropic thermal conductivity, filling simulations for determining local orientation of fillers, to calculate the directional dependency of thermal conductivity in a component
- a simulation tool that helps to design heat-dissipating plastic components by taking into account the part geometry, installation situation, heat input and air convection in the component's immediate proximity

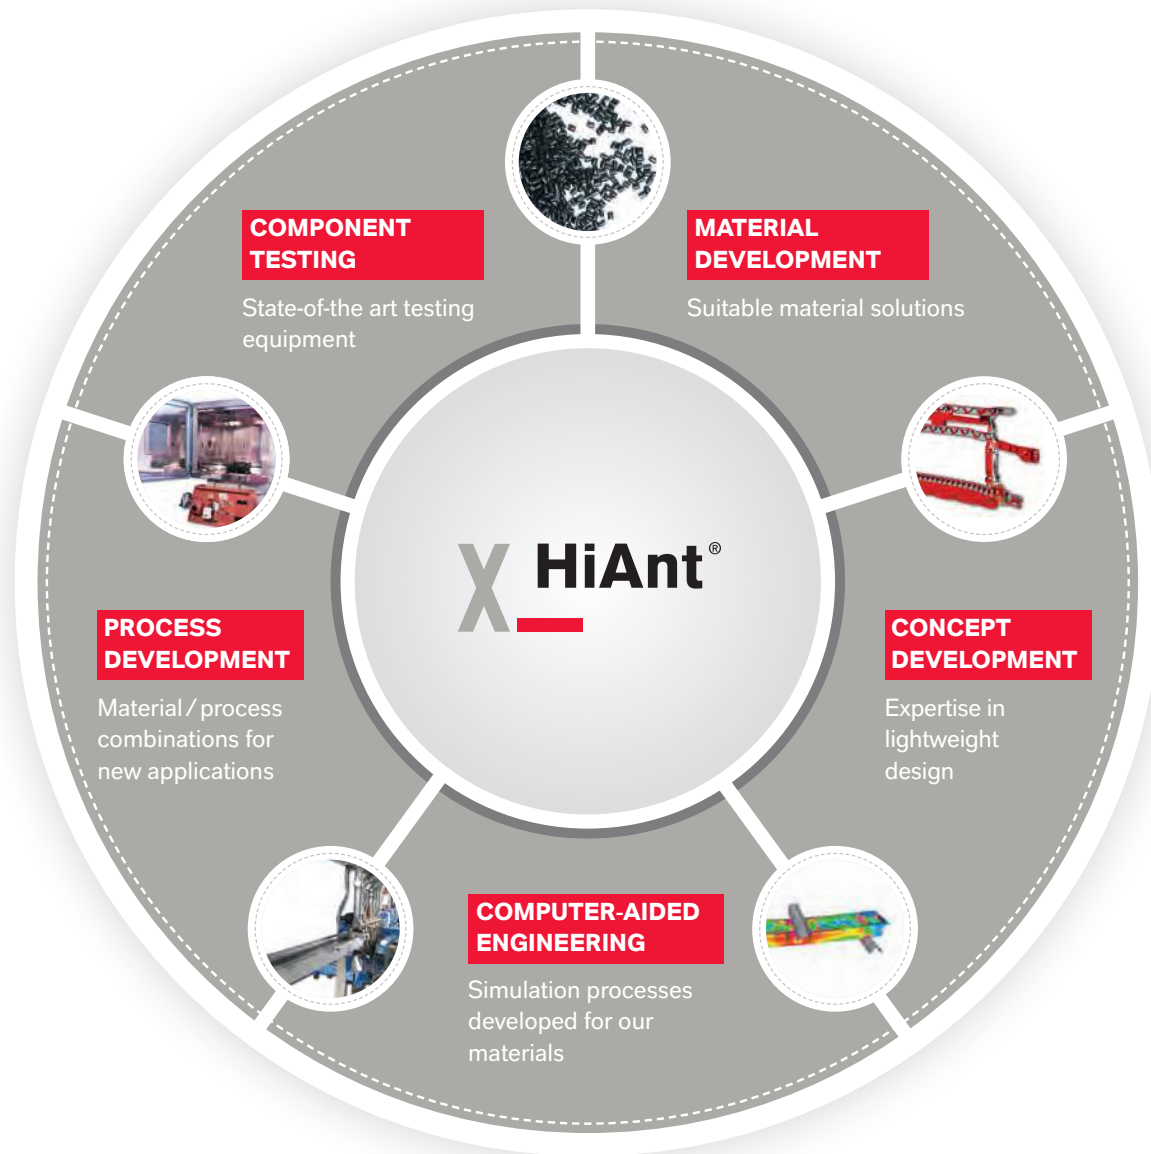

LIST OF IMPORTANT STANDARDS

- ¹ **UL 746C** "Standard for Polymeric Materials - Use in Electrical Equipment Evaluations"
- ² **DIN EN 60664-1** "Insulation coordination for equipment within low-voltage systems – Part 1: Principles, requirements and tests"
- ³ **DIN EN 60335-1** "Household and similar electrical appliances. Safety – Part 1: General requirements"
- ^{4a} **IEC 60695-2-11** "Fire hazard testing – Part 2-11: Glowing/hot-wire based test methods – Glow-wire flammability test method for end-products (GWEPT)"
- ^{4b} **IEC 60695-2-12** "Fire hazard testing – Part 2-12: Glowing/hot-wire based test methods – Glow-wire ignition temperature test method for materials (GWFI)"
- ^{4c} **IEC 60695-2-13** "Fire hazard testing – Part 2-13: Glowing/hot-wire based test methods – Glow-wire ignition temperature test method for materials (GWIT)"
- ⁵ **DIN EN 60695-11-10** "Fire hazard testing – Part 11-10: Test flames – 50 W horizontal and vertical flame test methods"
- ⁶ **UL94** "Tests for Flammability of Plastic Materials for Parts in Devices and Appliances"
- ^{7a} **EN 45545-1** "Railway applications - Fire protection on railway vehicles - Part 1: General"
- ^{7b} **DIN EN 45545-2** "Railway applications - Fire protection on railway vehicles - Part 2: Requirements for fire behavior of materials and components"
- ⁸ **DIN EN ISO 5659-2** "Plastics - Smoke generation - Part 2: Determination of optical density by a single-chamber test"
- ⁹ **NF X70-100** "Fire tests – Analysis of gaseous effluents – Part 2: Tubular furnace thermal degradation method"
- ¹⁰ **CSA C22.2 / No. 0.17-92** "Evaluation of Properties of Polymeric Materials – General Requirements; Part 4: Flame Test Procedure"
- ¹¹ **ISO 4589-1** "Plastics – Determination of burning behavior by oxygen index – Part 1: Guidance"
- ¹² **ASTM D 2863** "Standard test method for Measuring the Minimum Oxygen Concentration to Support Candle-Like Combustion of Plastics (Oxygen Index)"
- ¹³ **DIN EN 60695-11-5** "Fire hazard testing – Part 11-5: Test flames - Needle-flame test method - Apparatus, confirmatory test arrangement and guidance"
- ¹⁴ **UL 746A** "Polymeric Materials – Short Term Property Evaluations"
- ¹⁵ **DIN EN 60112** "Method for the determination of the proof and the comparative tracking indices of solid insulating materials"
- ¹⁶ **ASTM D 2303** "Standard Test Methods for Liquid-Contaminant, Inclined-Plane Tracking and Erosion of Insulating Materials"
- ¹⁷ **ASTM D 495** "Standard Test Method for High-Voltage, Low Current, Dry Arc Resistance of Solid Electrical Insulation"
- ¹⁸ **DIN EN 60243-1** "Electric strength of insulating materials - Test methods - Part 1: Tests at power frequencies"
- ¹⁹ **DIN IEC 60093** "Methods of test for insulating materials for electrical purposes; volume resistivity and surface resistivity of solid electrical insulating materials"
- ²⁰ **IEC 60250** "Recommended methods for the determination of the permittivity and dielectric dissipation factor of electrical insulating materials at power, audio and radio frequencies including meter wavelengths"
- ²¹ **UL 746B** "Polymeric Materials – Long Term Property Evaluations"
- ²² **IEC 60216-1** "Electrical insulating materials - Properties of thermal endurance – Part 1: Aging procedures and evaluation of test results"
- ²³ **DIN EN ISO 22007** "Plastics – Determination of thermal conductivity and thermal diffusivity – Part 1: General principles (ISO 22007-1:2009); German version EN ISO 22007-1:2012"
- ²⁴ **DIN 5036** "Radiometric and photometric properties of materials; methods of measurement for photometric and spectral radiometric characteristics"

